

Influence of Natural Fillers on Tribological and Mechanical Performance of Polyester Composites

Ibrahim R. A. *

Mechanical Engineering Department, Faculty of Engineering, Beni-Suif University, Beni-Suif, Egypt

Abstract

Polymer composites reinforced by natural fibers/fillers provide good tribological properties nontraditional materials for industrial applications that require desire friction coefficient and wear resistance such as bearing materials, brake pads materials and flooring materials ...etc. In the present work, polyester composites filled with Corn Straw Powder (CSP) or Jasmine Leaves Powder (JLP) proposed as new engineering materials with improved mechanical and frictional behavior. Cylindrical pins with 10 mm diameter and 30 mm height were prepared as test specimens. Two factors considered when designing the experiment; first the size of filling particles, second the weight ratio of the added particles. A Pin-on-disk tribometer designed and constructed to perform measurements of the friction coefficient and wear rate for proposed composites. WP300.20 universal testing device used to investigate the mechanical properties of polyester composite. Results show that corn straw particles and jasmine leaves powder have a significant effect on the mechanical and tribological behavior of polyester composites.

Keywords

Corn Straw Powder (CSP), Jasmine Leaves Powder (JLP), Polyester Composite, Friction, Wear, Stress- Strain Curve

Received: December 28, 2015 / Accepted: January 5, 2016 / Published online: April 5, 2016

© 2016 The Authors. Published by American Institute of Science. This Open Access article is under the CC BY license.

<http://creativecommons.org/licenses/by/4.0/>

1. Introduction

In the recent decade, polymers have become attractive materials for various applications due to several attractive properties, including light weight, ease of processing and cost-effectiveness. Hence, attempts have been significantly made to utilize polymers in different industrial applications, using various kinds of reinforcements including fibers that are incorporated into the polymers to increase their physical and mechanical properties. Thus, fiber reinforced polymer matrix composites are extensively attractive due to their light weight, biodegradability [1], high strength [2, 3], high stiffness [4], good corrosion resistivity [5], and low friction coefficient [6] in many applications that are important in mechanical and tribological properties, from households to aerospace applications and, today, these materials are used in

nearly all areas of daily life [7–16]. Agricultural wastes (A. W.) added as reinforcement materials for polyester resin. Tribological properties investigated for the proposed composites. The results show that agricultural wastes have a significant effect on the friction coefficient and wear rates of polyester composites [18]. Short fiber reinforced polymer composites used nowadays in numerous tribological applications. In spite of this fact, new developments are still under way to explore other fields of application for these materials and to tailor their properties for more extreme loading conditions. Polyester composites commonly used in industrial applications such as bearing materials, brake pads materials and flooring materials. Fiber Reinforced Plastics (FRP) are widely used as structural materials in the manufacture of, for example, marine boats, automobiles and bathtubs due to their light weight, high degree of rigidity and superior moldability. There are the two main characteristics

* Corresponding author

E-mail address: Refai95@yahoo.com

which make these materials attractive compared to conventional metallic designs. They are of relatively low density and they can be tailored to have stacking sequences to provide high strength and stiffness in directions of high loading. Composite materials consist of a resin and reinforcement chosen according to desired mechanical properties and the application. Polyesters also commonly used as matrix materials, particularly with glass-fibre-reinforcement. Polyester is an economic material that has high chemical resistance and is resistant to environmental effects. It has high dimensional stability and low moisture absorption. The production technologies for thermoset glass/polyester composites are easier and cheaper than those for other glass/resin materials. Glass-fibre-reinforced polymer with thermosetting polyester resin is an attractive material that is economically desirable. Its application at low temperatures and under service terms is easy when this material is compared to advanced polymer composites with a complex molecule structure, high strength and working under terms of difficult service, [19-24]. Fibre-Reinforced-Polymer composites are used particularly in the automotive and aircraft industries and the manufacture of spaceships and sea vehicles [25]. In industrial applications, the increase in the use of composite materials means that it is necessary to know their behaviour under working conditions. Wear and friction are an important parameters and their experimental behaviour must be known. Polymers frequently used in tribological applications because of their self-lubricating ability and loadability. However, most research on their friction and wear mechanisms is performed on small-scale test samples under relatively low normal loads, [26]. Polymers have been favorably introduced as sliding materials in offshore structures for over ten years because of good wear resistance. Mainly under high loads, surface plasticity contributes to low friction, which is favorable for a reduction in dissipated sliding energy, [27].

In the present work, polyester composites reinforced with Corn Straw Powder (CSP) proposed as new engineering materials with improved mechanical and frictional behavior.

2. Experimental

The investigation carried out to detect the effect of adding corn straws or jasmine leaves on the mechanical and tribological properties of polyester.

2.1. Raw Materials

Polyester risen (commercial name SIR RESIN from SABIC KSA) as a polymeric matrix and, Natural filler in form of powder of corn straws and jasmine dry leaves were supplied as agricultural waste from the plants, these wastes cleaned

from any other contaminates and grinded into two scales of particle size; soft particles with 0.5 mm particle size and coarse type with 3 mm particle size.

2.2. Preparation of Test Specimens

Polyester resin as a matrix material hand mixed – by means of a long wooden stirrer - with proposed filler powder in volumetric ratio up to 50% and mixed with its corresponding hardener by ratio of 3:1. After well mixing of the composite contents for 3 to 5 minutes it poured into cylindrical mold (30 mm height and 10 mm diameter) under ambient conditions of temperature, humidity and pressure, after 24 hours test specimens become completely solid and ready for measurements. All test specimens subjected to soft sandpaper for cleaning the surfaces and remove irregular layers for performing the tribological measurements. It was observed that there is a symmetrical distribution of the filling powder on the projected area of polyester composites, which mean that there are different amount of fillers on the surface of composite vary from 0% to 50% of the contact surface.

2.3. Description of Test Rig

Experiments carried out by means of pin-on-disk tribodevice for tribological measurements in form of coefficient of friction and rate of wear for the proposed composites. This device designed and constructed to perform this work. Pin-on disc consists of variable speed motor 170 rpm, steel counterface with 0.13 μm Ra and wear track of 90 mm diameter, pins holder with load cell for friction force detection connected with digital screen. Tests carried out at ambient conditions of temperature and humidity at 0.8 ms^{-1} sliding speed. Friction coefficient of polyester composites in dry contact with rotating steel disc were measured under different applied loads from 2 to 6 N. Polyester composites were held in specimen holder and loaded against the rotating steel counterface; the friction force was monitored by the digital screen which attached with the load cell. Figure 1 shows the surface of worn specimens. Friction coefficient calculated by dividing the friction force by the applied load, eq. (1).

$$\mu = F_f / F_n \quad (1)$$

Where,

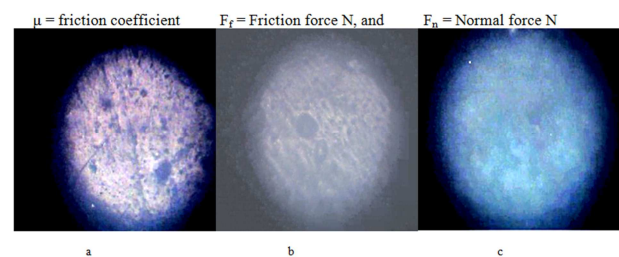


Fig. 1. a) unfilled polyester, b) polyester reinforced by soft particles and c) polyester reinforced by coarse particles.

2.4. Mechanical Measurements

A compression test carried out for the composite pins to indicate the effect of corn straw or jasmine leaves content upon the stress-strain behaviour of the proposed composite. Mechanical investigations performed by means of WP 300.20 universal testing machine under load range from 0 to 5 KN. A stress-strain curve plotted directly by the testing device for each test sample.

3. Results and Discussion

3.1. Tribological Effect of Corn Straw Particles

Figure 2 shows that increase of coarse particles of corn straw contents decreases slightly the friction coefficient of polyester composite from 0.75 for free specimen under 6 N applied load to 0.51 for composite reinforced by 15% coarse particle corn straw, then the friction coefficient increase to 0.58 with increases of corn straw contents to 50%. The friction reduction may be explained as a result of the contact between the counter face material and corn straw particles, which come to the contact zone. However, the friction coefficient increases for composite with high corn straw contents, which may be a result of the contact between the composite surface and transferred layer from the composite surface to the counter face.

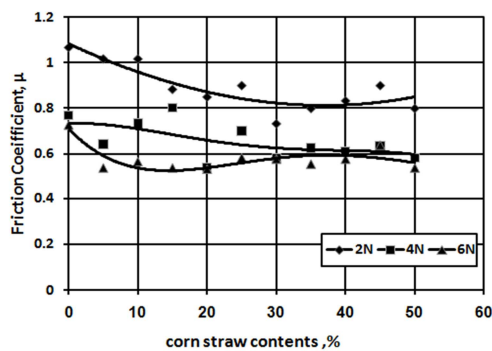


Fig. 2. Effect of coarse corn straw particles on the friction coefficient of polyester composites.

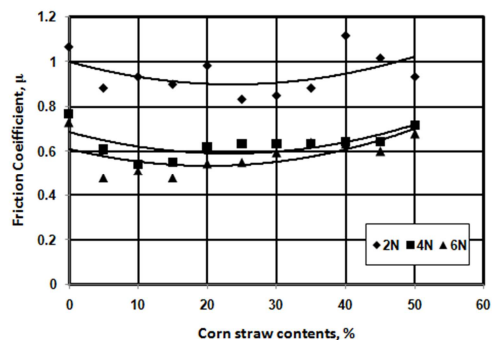


Fig. 3. Effect of soft corn straw particles on the friction coefficient of polyester composites.

Figure 3 shows that increase of soft particles of corn straw content slightly decreases the friction coefficient of polyester composites from 1.02, 0.79 and 0.75 for free specimen under 2, 4 and 6 N applied load respectively to 0.9, 0.58 and 0.48 for composite reinforced by 15% soft particle corn straw under 2, 4 and 6 N respectively, then the friction coefficient increase under all loads with increases of corn straw contents to 45%.

It seems that there is an elastic deformation occurred on the composite surface under high loads, which may be responsible for the friction reduction. It can be concluded that the transferred layer responsible for the increase of friction for composite with high corn straw contents. These results show that there is no significant effect for the particle size on the friction coefficient of proposed composite. Figure 4 shows the rate of wear in grams per minute for polyester composites filled with coarse or soft corn straw. As shown in figure both coarse and soft particles of corn straw decreases the rate of wear for polyester composites, wear rate decrease from 0.03 g/min. for polyester free of corn straw to 0.01 g/min. with increases of soft corn straw to 25%. However, increase of coarse particles in polyester composite to 40% decrease the rate of wear to minimum value 0.005 g/min. It seems that increase of soft and coarse corn straw powder to 25% and 40% in polyester respectively increases the bonds between composite phases and decreases the amount of material losses.

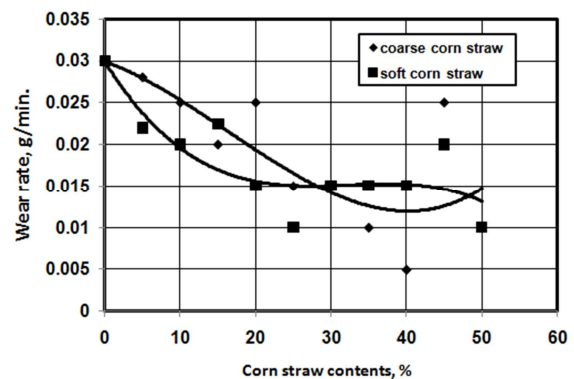


Fig. 4. Effect of corn straw content on the rate of wear of polyester composites.

3.2. Mechanical Effect of Corn Straw Particles

Figure 5 discusses the relation between stress and strain for the polyester composite reinforced by coarse particles of corn straw. As shown in the figure the ultimate strength of polyester composite increases from 48 N/mm² for free polyester to 100 N/mm² for polyester containing 5% and 30% corn straw particles, on the other hand the fracture strain of polyester increases from 0.8 for free specimen to 1.2 for polyester composite reinforced by 5% corn straw. Continuous

increasing of corn straw in polyester composites to 50 % decreases the strength of composite less than 40 N/mm² and decreases the fracture strain to less than 0.8, which may be a result of decreasing the bonding between the composite contents. Figure 6 shows that increase of soft particles of corn straw in polyester composite to 50% increases the ultimate strength to more than 70 N/mm² and increases the fracture strain to 1.2. From these results it can be seen that the optimum composites of polyester reinforced by corn straw is that composite which contains 5% coarse particles of corn straw and the composite which have 50% soft particles of corn straw, these two percentage improved the mechanical behavior of polyester composite.

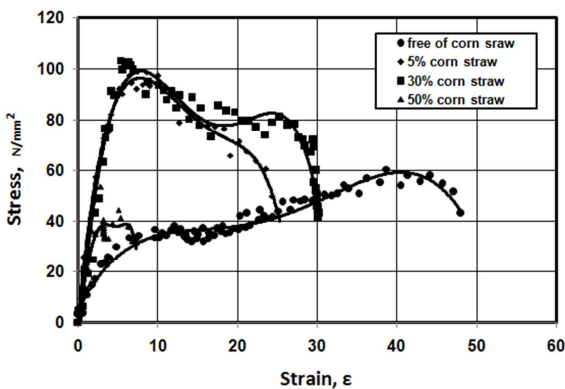


Fig. 5. Effect of coarse corn straw particles on the stress-strain curve of polyester composites.

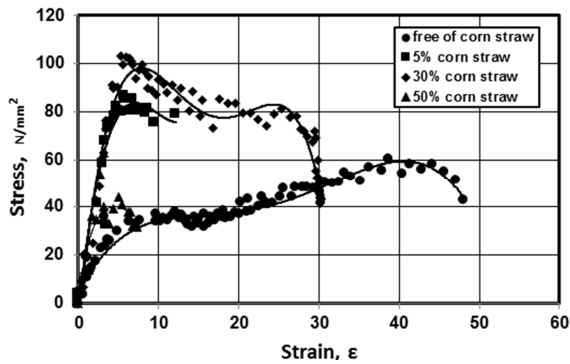


Fig. 6. Effect of soft corn straw particles on the stress-strain curve of polyester composites.

3.3. Tribological Effect of Jasmine Dry Leaves Particles

Figure 7 shows that the increase of soft particles contents of jasmine leaves in polyester composite caused an increase in friction coefficient. For instant, friction coefficient increased from 0.7 for polyester free of agricultural wastes to 1.0 for composite containing 30% jasmine leaves under the load of 4 N. This may be discussed on the basis that the particles of jasmine leaves formed an abrasive layer that increased friction coefficient.

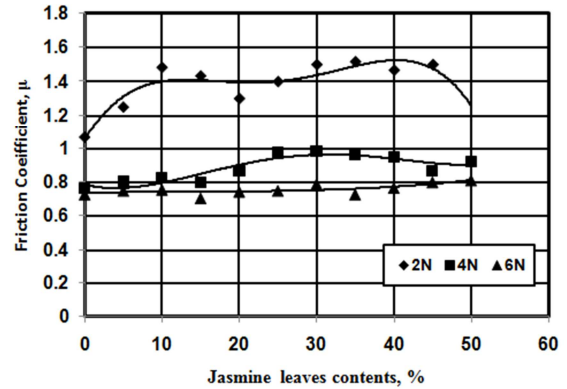


Fig. 7. Effect of soft jasmine leaves particles on the friction coefficient of polyester composites.

Figure 8 shows that increase of coarse particles of jasmine leaves increased friction coefficient from 0.7 for polyester free of agricultural wastes to more than 1.55 for composite containing 50 % jasmine leaves under 2 N load. Figure 9 shows that the increase of soft particles content of jasmine leaves in polyester composites decreased wear rate from 0.02 g/min to 0.008 g/min. It is shown that wear rate of polyester filled by coarse jasmine leaves slightly exceeded wear rate of composites filled by soft particles.

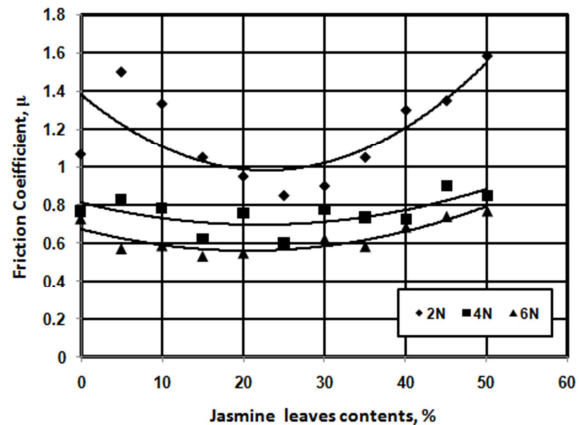


Fig. 8. Effect of coarse jasmine leaves particles on the friction coefficient of polyester composites.

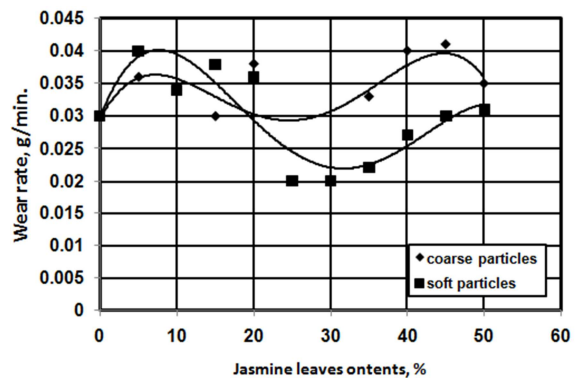


Fig. 9. Effect of jasmine leaves particles on the wear rate of polyester composites.

3.4. Mechanical Effect of Jasmine Dry Leaves Particles

Figure 10 shows the stress-strain curve for polyester free of agricultural wastes, as shown in this figure the ultimate stress of polyester is approximately 60 N/mm^2 .

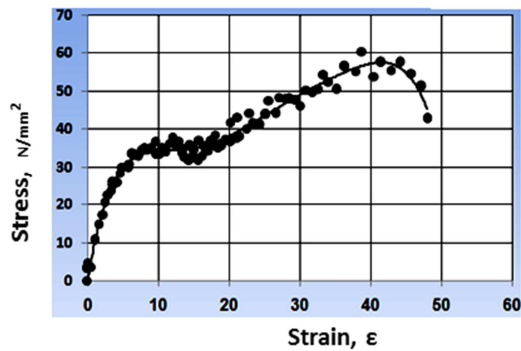


Fig. 10. Stress – strain curve for polyester free of jasmine leaves.

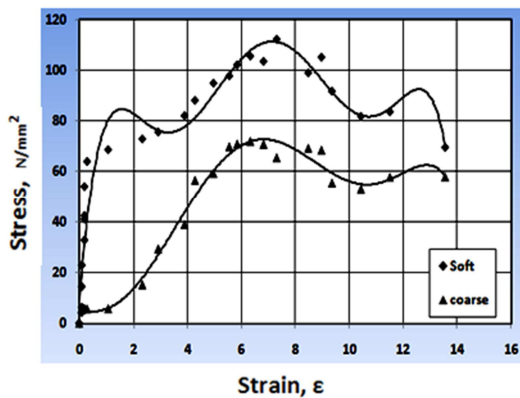


Fig. 11. Stress – strain curve for polyester composite filled with 5 wt. % jasmine leaves.

As represented in Fig. 11 increases of jasmine leaves in polyester composite increase the ultimate strength for polyester composite to more than 110 N/mm^2 for composite filled by 5% soft particles of jasmine leaves wastes; beside slightly increases of ultimate strength to 72 N/mm^2 for composite filled by 5 % coarse particles of jasmine leaves.

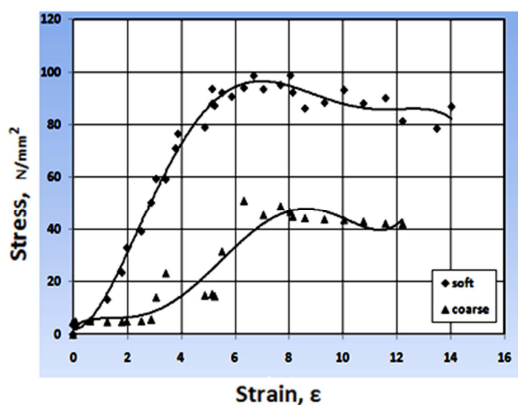


Fig. 12. Stress – strain curve for polyester composite filled with 30 wt. % jasmine leaves.

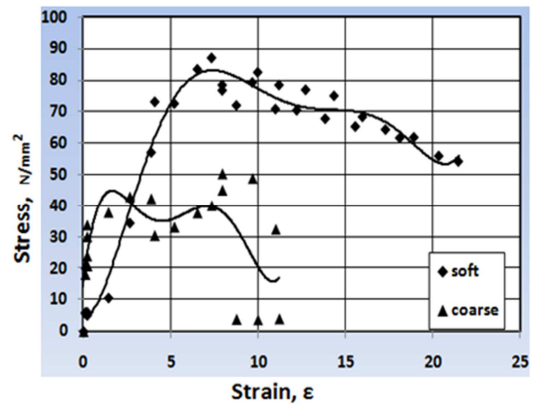


Fig. 13. Stress – strain curve for polyester composite filled with 50 wt. % jasmine leaves.

Figure 12 shows that increase of wastes to 30 % increases the ultimate strength of polyester composite from 60 N/mm^2 to more than 90 N/mm^2 for composite filled by soft particles of wastes. But on the other hand increase of coarse particles of jasmine leaves in polyester composite to 30% decreases the ultimate strength to 48 N/mm^2 , which mean that the composite become weaker than free polyester.

Polyester composites filled by 50% soft particles of jasmine wastes have ultimate strength of 85 N/mm^2 ; beside the increases of coarse particles of wastes in composites to 50% make the composite weaker than free polyester as shown in Fig. 13.

4. Conclusions

From this work it can be concluded that:

1. The friction coefficient of polyester can be decreased with the increase of corn straw content in the polyester composites.
2. Wear rate of polyester composites decreases to 0.005 g/min . with increase of corn straw contents to 40%.
3. The mechanical behavior of polyester can be improved by adding corn straw particles to polyester in form of coarse particles by 5% of the composite weight.
4. Use of agricultural wastes (corn straw) can improve the mechanical and tribological behavior of polyester composites which can be used in industrial applications.
5. The friction coefficient of polyester composite increases with increasing the content of coarse particles of jasmine leaves in composites under low loads.
6. Increase of soft particles of jasmine leaves in polyester composites remarkably decreases the rates of wear for proposed composites.
7. Polyester composites filled with jasmine leaves were recommended as high friction and low wear rates material

for industrial applications such as brake linings.

8. Addition of jasmine leaves improves the mechanical behavior of polyester composites.
9. Ultimate strength of polyester composites increases remarkably to 110 N/mm² and 90 N/mm² with increasing the content of soft particles of jasmine leaves in polyester composites to 5% and 30% respectively.
10. Increasing the content of coarse particles of jasmine leaves in composites to 50% makes the composites weaker than free polyester.

References

- [1] V. K. Thakur, M. K. Thakur, R. K. Gupta, Review: raw natural fiber-based polymer composites, *Int. J. Polym. Anal. Charact.* 19 (2014) 256-271.
- [2] H. Ku, H. Wang, N. Pattarachaiyakoo, M. Trada, A review on the tensile properties of natural fiber reinforced polymer composites, *Compos. Part B Eng.* 42 (2011) 856-873.
- [3] B. Barari, T. Ellingham, I. Qamhia, K. Pillai, R. El-Hajjar, L.-S. Turng, et al., Mechanical characterization of scalable cellulose nano-fiber based composites made using liquid composite molding process, *Compos. Part B Eng.* (2015) doi:10.1016/j.compositesb.2015.08.040.
- [4] C. Unterweger, O. Brüggemann, C. Fürst, Synthetic fibers and thermoplastic short-fiber-reinforced polymers: properties and characterization, *Polym. Compos.* 35 (2014) 227-236.
- [5] T. Santos, G. Vasconcelos, W. de Souza, M. Costa, E. Botelho, Suitability of carbon fiber-reinforced polymers as power cable cores: Galvanic corrosion and thermal stability evaluation, *Mater. Design* 65 (2015) 780-788.
- [6] X.-Q. Pei, R. Bennewitz, A. K. Schlarb, Mechanisms of friction and wear reduction by carbon fiber reinforcement of PEEK, *Tribol. Lett.* 58 (2015) 1-10.
- [7] S. Bahadur, Y. Zheng, Mechanical and tribological behavior of polyester reinforced with short glass fibers, *Wear* 137 (1990) 251-266.
- [8] S. Zhang, State-of-the-art of polymer tribology, *Tribol. Int.* 31 (1998) 49-60.
- [9] K. Friedrich, Z. Zhang, A. K. Schlarb, Effects of various fillers on the sliding wear of polymer composites, *Compos. Sci. Technol.* 65 (2005) 2329-2343.
- [10] D. L. Burris, B. Boesl, G. R. Bourne, W. G. Sawyer, Polymeric nanocomposites for tribological applications, *Macromol. Mater. Eng.* 292 (2007) 387-402.
- [11] Y. Zhang, S. Zhu, Y. Liu, B. Yang, X. Wang, The mechanical and tribological properties of nitric acid-treated carbon fiber-reinforced polyoxymethylene composites, *J. Appl. Polym. Sci.* 132 (2015).
- [12] V. Dhand, G. Mittal, K. Y. Rhee, S.-J. Park, D. Hui, A short review on basalt fiber reinforced polymer composites, *Compos. Part B Eng.* 73 (2015) 166-180.
- [13] E. Omrani, B. Barari, A. Dorri Moghadam, P. K. Rohatgi, K. M. Pillai, Mechanical and tribological properties of self-lubricating bio-based carbon-fabric epoxy composites made using liquid composite molding, *Tribol. Int.* 92 (2015) 222-232. doi:10.1016/j.triboint.2015.06.007.
- [14] I. Avdeev, M. Gilaki, Structural analysis and experimental characterization of cylindrical lithium-ion battery cells subject to lateral impact, *J. Power Sources* 271 (2014) 382-391.
- [15] P. Yang, S. S. Shams, A. Slay, B. Brokate, R. Elhajjar, Evaluation of temperature effects on low velocity impact damage in composite sandwich panels with polymeric foam cores, *Compos. Struct.* 129 (2015) 213-223.
- [16] P. L. Menezes, S. V. Kailas, M. R. Lovell, Friction and transfer layer formation in polymer-steel tribo-system: role of surface texture and roughness parameters, *Wear* 271 (2011) 2213-2221.
- [17] Ibrahim R. A., "Tribological performance of polyester composites reinforced by agricultural wastes", *Journal of tribology international*, 90, pp. 263-266, (2015).
- [18] Ibrahim R. A., Ali W. Y., "Tribological performance of polyester composites filled by vegetable oil", *Journal of material science and engineering technology*, 5, pp. 287-292, (2010).
- [19] Karger-Kocsis J., Zhang Z., "Structure-property relationships in nanoparticle/semi-crystalline thermoplastic composites". Mechanical properties of polymers based on nanostructure and morphology, New York: CRC Press; pp. 547-596, (2005).
- [20] Gauthier C., Schirrer R., "Time and temperature dependence of the scratch properties of poly (methylmethacrylate) surfaces", *Journal of Materials Science*, 35(9), pp. 2121-2130, (2000).
- [21] Neogi S., Hashmi S. A. R., Chand N., "Role of PET in improving wear properties of PP in dry sliding condition Bull", *Mater. Sci.*, 26, p. 579, (2003).
- [22] Franklin S. E., "Wear experiments with selected engineering polymers and polymer composites under dry reciprocating sliding conditions", *Wear*, 251, p. 1591, (2001).
- [23] Hashim P., Nihat T., "Investigation of the wear behaviour of a glass-fibre-reinforced composite and plain polyester resin", *Composites Science and Technology*, 62, pp. 367-370, (2002).
- [24] Beake B. D., Leggett G. J., Shipway P. H., "Nanotribology of biaxially oriented poly(ethylene terephthalate) film", *Polymer* 42, p. 7025, (2001).
- [25] Branco J. R. T., Campos S. V., "Wear behaviour of thermally sprayed PET", *Surf. Coat. Technol.*, 676, pp. 120-121, (1999).
- [26] Samyn P., Baets P., "Friction of polyoxymethylene homopolymer in highly loaded applications extrapolated from small-scale testing", *Tribol. Lett.*, 19, pp. 177-189, (2005).
- [27] Inoue, Kaoru M. Y., "Development of the chemical recycling technology of glass fiber reinforced PA6 Parts", *SAE Paper*, 01, p. 0694, (2001).